

Experimental Investigation on Silica Fume as partial Replacement of Cement in High Performance Concrete

¹T.Shanmugapriya , ²Dr.R.N.Uma

¹Department of Civil Engineering,
Sri Ramakrishna Institute of Technology, Coimbatore -10, India.
²Department of Civil Engineering,
Sri Ramakrishna Institute of Technology, Coimbatore -10, India.

-----ABSTRACT-----

With increased environmental awareness and its potential hazardous effects, utilization of industrial byproducts has become an attractive alternative to disposal. Silica fume(SF), which is byproduct of the smelting process in the silicon and ferrosilicon industry. Silica fume is very effective in the design and development of high performance concrete. This paper presents the results of an experimental investigations carried out to find the suitability of silica fume in High Performance concrete. The concrete used in this investigation was proportioned to target a mean strength of 60 MPa and designed as per ACI 211.4R-08. The water binder ratio (W/B) adopted was 0.32 and the Super Plasticizer used was CONPLAST SP 430. Specimens such as cubes, beams and cylinders were cast for various mix proportions and tested at the age of 7, 14 and 28 days. The investigation revealed that the partial replacement of cement by silica fume will develop compressive strength, flexure strength and split tensile strength sufficient for construction purposes. The optimum dosage of silica fume found to be 7.5% (by weight), when used as partial replacement of ordinary Portland cement. Its use will lead to a reduction in cement quantity required for construction purposes and hence sustainability in the construction industry as well as economic construction.

KEY WORDS: *Compressive strength, Flexure strength, High Performance Concrete, Silica fume, Split Tensile strength*

Date of Submission: 25, May, 2013



Date of Publication: 5, June, 2013

I. INTRODUCTION

High Performance Concrete (HPC) has been developed over the last two decades, and was primarily introduced through private sector architectural design and construction such as high rise buildings and parking garages. HPC is used for concrete mixtures, which possess high workability, high strength, high modulus of elasticity, high density, high dimensional stability, low permeability and resistance to chemical attack. According to ACI “High Performance Concrete is defined as concrete which meets special performance and uniformity requirements that cannot always be achieved routinely by using conventional materials and normal mixing, placing and curing practices”.

The supplementary cementitious materials (SCMs) such as silica fume, fly ash and ground granulated blast furnace slag are more commonly used mineral admixtures in the development of HPC mixes. They generally used to resist compressive forces and also due to its pozzolanic action the properties of High Performance Concrete viz, workability, durability, strength, resistance to cracks and permeability can be improved.[1] Silica Fume is most commonly used supplementary cementitious materials used in the development of High Performance Concrete. Silica fume (SF) is a byproduct of the smelting process in the silicon and ferrosilicon industry. It is also known as micro silica, condensed silica fume, volatilized silica or silica dust. Silica fume colour is either premium white or grey. Silica Fume consists of very fine vitreous particles with a surface area between 13,000 and 30,000 m²/kg. Its particles are approximately 100 times smaller than the average cement particle. Because of its extreme fineness and high silica content, silica fume is a highly effective pozzolanic material. Silica fume is used in concrete to improve its properties. It has been found that silica fume improves compressive strength, bond strength, and abrasion resistance; reduces permeability; and therefore helps in protecting reinforcing steel from corrosion.[2] When Silica fume are incorporated to concrete, the silica present in these materials react with the calcium hydroxide released during the hydration of cement and forms additional calcium silicate hydrate (C – S – H), which improve durability and the mechanical properties of concrete.[3]

High compressive strength is generally the first property associated with silica fume concrete. The addition of silica fume to a concrete mix will increase the strength of that mix by between 30% and 100% depending on the type of mix, type of cement, amount of silica fume, use of plasticizers, aggregate types and curing regimes.[4] Silica fume concrete is very susceptible to temperature variations during the hardening process. The optimum silica fume content to achieve higher strengths seems to range between 15 and 20%. [5] There are three mechanisms namely (i) Strength enhancement by pore size refinement and matrix densification, (ii) Strength enhancement by reduction in content of CH and (iii) Strength enhancement by cement paste- aggregate interfacial refinement are believed to be responsible for the strength development of concrete and mortars containing silica fume. [6]

High range water reducing admixtures (Super plasticizer) is used as a part of chemical admixtures in High Performance Concrete to produce better workability and high strengths. The brief literature on the study has been presented in following text. The influence of silica fume in replacement of cement on physical properties and resistance to sulphate attack, freezing and thawing, and alkali silica reactivity and the maximum 28 days compressive strength was obtained at 15% silica fume replacement level, at a W/C ratio of 0.35 with variable dosages of HRWRA. [7] High Performance Concrete with silica fume at a constant water binder ratio (w/b) of 0.34 and replacement percentages of 0 to 25, with varying dosages of HRWRA increases the compressive strength, the optimum percentage was obtained at 15% replacement level. Developing High Performance with a better understanding of the isolated contributions of silica fume on concrete over a wide range of w/c ratio ranging from 0.26 to 0.42 and cement replacement percentages from 0 to 30. [8] The main objective of this investigation is to minimize the usage of cement content to some proportion in the High Performance Concrete. This present work is to study various properties namely compressive strength, Split Tensile Strength and Flexure strength of M60 grade HPC mixes incorporating different percentages silica fume by weight of cement along with Sulphonated Naphthalene based super plasticizer (CONPLAST SP 430).

II. EXPERIMENTAL PROGRAMME

The Experimental Programme was designed to compare the mechanical properties of High Performance Concrete with M60 grade of concrete with different replacement levels of ordinary Portland cement 53 grade with silica fume. The replacement levels of cement by silica fume are selected as 2.5%, 5%, 7.5%, 10%, and 12.5%. The specimens of Cube specimen of size 150 x 150 x 150 mm, Cylinder specimen of size 150 mm diameter and 300 mm height and Beam specimen of size 100 x 100 x 500 mm were prepared with and without silica fume.

2.1 Materials Used

Cement: Ordinary Portland cement of 53 Grade was used and the specific gravity of cement was found to be 3.15.

Silica Fume (Grade 920 D): Obtained from ELKEM South Asia Pvt.Ltd.Mumbai, was named Elkem – micro silica 920 D conforming to ASTM C1240. The physical and chemical properties of cement and silica fume are given in Table.1

Table 1. Physical and chemical Properties of cement and silica fume

Properties	OPC	Silica fume
Physical		
Specific gravity	3.15	2.2
Specific area cm ² /gm	3250	1800000
Chemical		
Silicon di oxide(SiO ₂)	20.3	89.5
Aluminium oxide(Al ₂ O ₃)	6.3	1.2
Iron Oxide(Fe ₂ O ₃)	3.12	2
Calcium Oxide(CaO)	63.6	0.2-0.8
Magnesium Oxide(MgO)	1.6	0.2-0.8
Sodium Oxide(Na ₂ O)	0.4	0.5-1.2
Potassium Oxide(K ₂ O)	0.51	-
Loss of Ignition	1.13	3

Fine Aggregate: River sand having bulk density 1720 kg/m³ was used and the specific gravity was found to be 2.56. Sieve analysis results are shown in Table. 2

Table 2 Sieve analysis of River sand

Sieve Size	River sand % Passing
4.75mm	98
2.36mm	96
1.18mm	78
600µm	51
300 µm	26
150 µm	7

Coarse Aggregate: Crushed angular aggregate with maximum grain size of 12.5mm and down graded was used and having bulk density 1691kg/m³. The specific gravity and fineness modulus was found to be 2.78 and 2.75 respectively.

Super plasticizer: CONPLAST SP 430 was used as water reducing agent to achieve the required workability. It is based on SulphonatedNaphthalene polymers complies with IS 9103:1999 and ASTM C 494 type F as a high range water reducing admixture. It is a brown liquid instantly dispensable in water.

Water: Fresh portable water, which is free from acid and organic substance, was used for mixing the concrete.

2.2 Mix Proportioning

Concrete mix design in this investigation was designed as per the guidelines specified in ACI 211.4R-08 - “Guide for selecting proportions for high strength concrete with portland cement and other cementations materials”. [9] Six concrete mixtures with different proportions of silica fume ranging from 0% (for the control mix) to 12.5%. The mix proportions were calculated and presented in Table. 3

Table 3. Mixproportion for High Performance Concrete

Materials	Cement (%)	Silica Fume (%)	Cement (kg/m ³)	Silica Fume (kg/m ³)	Fine aggregate (kg/m ³)	Coarse aggregate (kg/m ³)	W/B Ratio
C	100	0	551.87	-	672	1149.8	0.32
SF 2.5%	97.5	2.5	532.35	13.8	672	1149.8	
SF 5%	95	5	512.51	27.59	672	1149.8	
SF 7.5%	92.5	7.5	492.66	41.39	672	1149.8	
SF 10%	90	10	472.5	55.19	672	1149.8	
SF 12.5%	87.5	12.5	453.6	68.98	672	1149.8	

2.3 Casting and curing of Test specimens:

The specimen of standard cube, Cylinder and beams were used to determine the compressive strength Split tensile and flexural strength of concrete. Three specimens were tested for 7, 14 & 28 days with each proportion of Silica fume replacement. For each measured quantities of coarse aggregate and fine aggregate was spread in a pan, the ordinary Portland cement (53 Grade) and silica fume were spread out over it, water was measured by considering the water binder ratio as 0.32 and weight of super plasticizer(CONPLAST SP 430) was estimated as 1.2 % of weight of binder. The exact quantity of water and super plasticizer was added. The concrete was thoroughly mixed until it achieved homogeneous and uniform consistency. The fresh concrete was cast in cube, cylinder and beam moulds, and was compacted by table vibrator. All freshly cast specimens were left in the moulds for 24 hours before being de moulded. The de moulded specimens were cured in water for 7, 14 & 28 days, were air dried and then tested for its compressive strength, Split tensile strength and flexural strength as per Indian standards.

III. RESULTS AND DISCUSSIONS

Compressive strength of concrete:

The test was carried out conforming to IS 516-1959 to obtain compressive strength of concrete at the age of 7, 14 and 28 days. The cubes were tested using Compression Testing Machine (CTM) of capacity 2000KN. The results are presented in Figure 1

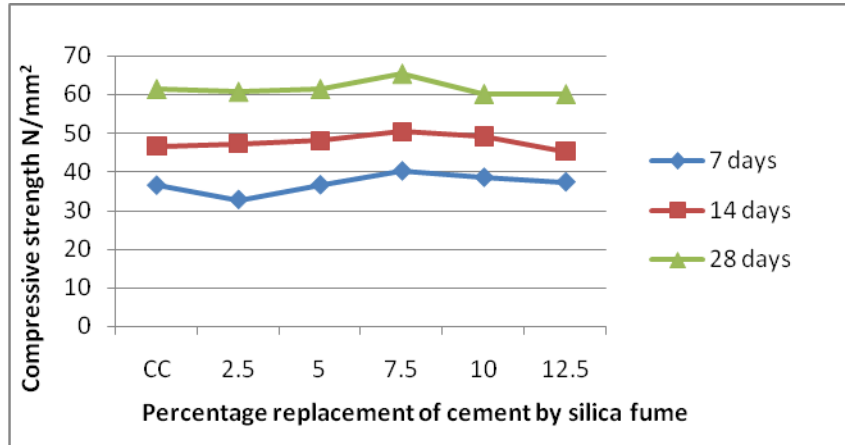


Fig. 1-Compressive Strength of High Performance Concrete Withvarious proportions of Silica fume

Fig. 1 shows the variation of compressive strength with silica fume replacement percentage. There is a significant improvement in the compressive strength of concrete because of the high pozzolanic nature of the silica fume and void filling ability. The compressive strength with replacement of cement by silica fume was increased 0% to 7.5% and then decreased. Hence the optimum silica fume was 7.5%. The optimum silica fume replacement percentage for obtaining maximum 28-day strength of concrete ranged from 5% to 20%. [10] The maximum value of compressive strength was obtained as 65.33MPa at 7.5% replacement of silica fume.

3.2 Split Tensile Strength of Concrete

The test was carried out conforming to IS 516-1959 to obtain split tensile strength of concrete at the age of 7, 14 and 28 days. The cylinders were tested using Compression Testing Machine (CTM) of capacity 2000KN. The results are presented in Figure 2.

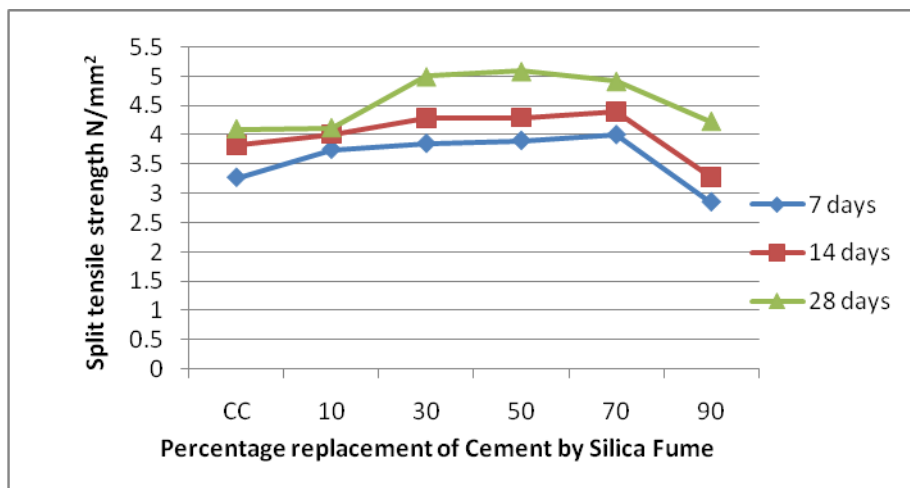


Fig 2.Split tensile Strength of High Performance Concrete Withvarious proportions of Silica fume

The Split tensile strength of the High Performance Concrete increases with the increase in percentage of Silica Fume. The partial replacement of 7.5% Silica fume is found to be optimum. High Performance Concrete at the age of 28 days with partial replacement of 7.5% cement by silica fume showed 20% greater Split tensile Strength than conventional concrete respectively.

3.3. Flexural strength of concrete:

The test was carried out conforming to IS 516-1959 to obtain Flexural strength of concrete at the age of 7, 14 and 28 days. The beams were tested using Flexure Testing Machine (FTM) of capacity 100KN. The results are presented in Figure.3

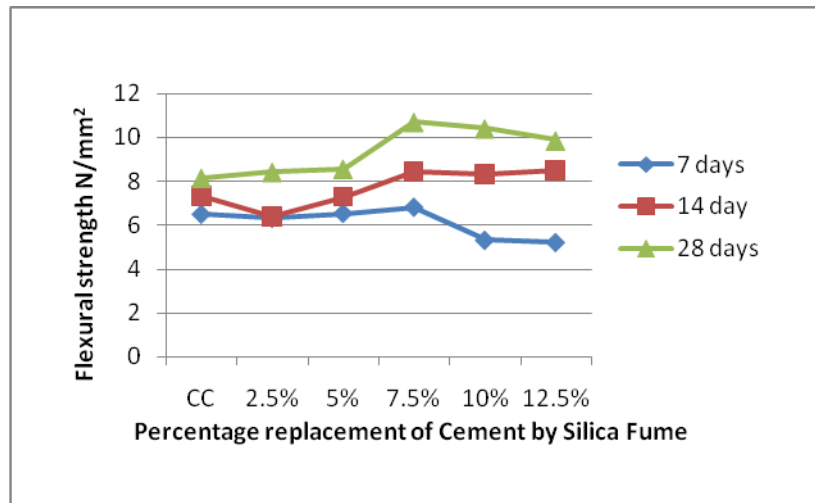


Fig 3. Flexural Strength of High Performance Concrete With various proportions of Silica fume

The flexural strength at the age of 28 days of silica fume concrete continuously increased with respect to controlled concrete and reached maximum value of 7.5% replacement level. High Performance Concrete at the age of 28 days with partial replacement of 7.5% cement by silica fume showed 23% greater flexural Strength than conventional concrete. It can be concluded that the ultra – fine silica fume particles, which consists mainly of amorphous silica, enhance the concrete strength by both pozzolanic and physical actions.

IV. CONCLUSIONS:

High performance concrete produced from cement replacement upto 7.5% silica fume leads to increase in compressive strength, split tensile and Flexure strength of concrete. Beyond 7.5 % there is a decrease in compressive strength, split tensile and Flexure strength of concrete. The compressive strength mainly depends on the percentage of silica fume because of its high pozzolanic nature to form more densely packed C-S-H gel. High Performance Concrete with silica fume can be effectively used in high rise buildings since high early strength is required, and the construction period can be reduced. The percentage of increase in the compressive strength is 15%, Split tensile strength is 20% and the flexure strength is 23% at the age of 28 days by replacing 7.5% of cement by silica fume. The optimum percentage of replacement of cement by silica fume is 7.5%

REFERENCES:

- [1] Sensale GR., Strength development of concrete with rice husk ash, *Cement and Concrete Composites*, 28(2), 2006, 158-160.
- [2] Mohammad Iqbal Khana and Rafat Siddiqueb, Utilization of silica fume in concrete: *Review of durability properties, Resources, Conservation and Recycling*, 2011, 57, 30-35
- [3] Igarashi S, Watanabe A and Kawamura M., Evaluation of capillary pore size characteristics in high-strength concrete at early ages. *Cement and Concrete Research*, 35(3), 2005, 513-519.
- [4] Bhanja, S. and Sengupta, B. (2002). "Investigations on the composite structure of silica fume concrete using statistical methods", *Cement and Concrete Research*, Vol. 32, pp. 1391-1394.
- [5] Aitcin, P.C., and Laplante, P. (1990). "Long-term compressive strength of silica fume concrete", *Journal of Materials in Civil Engineering*, Vol. 2, No. 3, pp. 164-170.
- [6] Feldman, R.F., Cheng-yi, H. (1985). "Properties of Portland cement silica fume pastes. II mechanical properties", *Cement and Concrete Research*, Vol. 15 No. 6, pp. 943.
- [7] Yogendran V, Langan BW, Haque M and Ward MA. Silica on high strength concrete, *ACI Material Journal*, No. 2, 84(1987) 124 – 129.

- [8] Bhanja S, Sengupta B. Optimum silica fume content and its mode of action on concrete, *ACI Materials Journal*, September – October 2003, pp. 407 – 712.
- [9] ACI Committee 211.4R.93, “Guide for Selecting properties for High Strength Concrete with Portland Cement and Fly ash” *ACI manual of concrete Practice*, 2001.
- [10] S.A. Khedr, M.N and Abou-Zeid, Characteristics of silica-fume concrete, *J. Mater. Civ. Eng. ASCE* 6 (3), 1994, 357–375.